



PROPERTIES OF FUEL BRIQUETTES AFTER THREE YEARS STORAGE

A. Nováková, M. Brožek

Department of Material Science and Manufacturing Technology, Faculty of Engineering, Czech University of Life Sciences Prague, Czech Republic

Abstract

The paper presents the results of laboratory tests intent on the study of storage place, placing manner and storage time on mechanical properties of briquettes made from spruce sawdust. The briquettes properties were evaluated by their density and rupture force determination. Moreover the mechanical durability, the gross calorific value, the total moisture and the ash content were determined. By the carried out tests it was univocally proved that the mode of storage influences briquettes durability at their long-term storage most of all. On the basis of the carried out tests it is possible to state that for the parameter of briquettes quality evaluation the rupture force can be recommended.

Key words: spruce sawdust, gross calorific value, density, rupture force, moisture content, mechanical durability.

INTRODUCTION

Briquetting is a relatively old technology. The first mentions of their use have been published in the first half of the 18th Century. The Otto's Encyclopedic Dictionary (OTTO, 1891) describes relatively lengthily the basis and the use of briquetting and of briquettes in practice. The mention of briquetting technology and of briquettes can be found practically in all older as well in newly domestic (STEHLÍK ET AL., 1966; VŠEOBECNÁ ENCYKLOPEDIJE, 1999) as well as in foreign encyclopedias (ENCYCLOPEDIA BRITANNICA, 1991).

In the twenty last years in the Czech Republic the briquetting technology asserted oneself in the field of metallic and non-metallic processing, too. The basis of this method is the high pressure effect on a fine-grained material. Briquettes, most often of cylindrical form and various diameter and length, are the final product. But briquettes can be of various shape, e.g. of cuboid with rounded corners, of hexagonal cuboid etc., according to the design of the press chamber of the used briquetting press.

MATERIALS AND METHODS

On briquettes from wood waste determined for combustion a row of demands are laid, which are specified in relevant national directives. In the Czech Republic the demands on briquettes properties are prescribed by the Directive of Ministry of the Environment Nr. 14-2009. It demands the briquettes minimum density of $900 \text{ kg}\cdot\text{m}^{-3}$. The briquettes strength demands are not prescribed. Nevertheless for operational reasons the adequate compactness is very important in order that at a common handling neither crumbling

The use of briquetting technology can bring substantial savings. Waste pressed from flammable materials, e.g. from wood waste (chips, sawdust), straw, coal, paper, cellulose, tobacco etc. is mostly utilized energetically (by combustion) (BASORE, 1929; PLÍŠTIL ET AL., 2004; BROŽEK, 2011; BROŽEK ET AL., 2012; BROŽEK AND NOVÁKOVÁ, 2013). After its compression the waste from combustible materials, e.g. dust collected on air filters, abrasion dust or chips from cutting of metals and their alloys (ČSN 42 0030, 1994; ČSN 42 1331, 1991) is better usable. After compression the waste volume strongly decreases. This makes easy its handling and decreases costs in transport or storage on a waste disposal site. The aim of carried out experiments has been to assess the properties of the newly made briquettes and of briquettes stored during three years under suitable and less suitable conditions.

nor disintegration occur. The briquettes minimum gross calorific value must be $17 \text{ MJ}\cdot\text{kg}^{-1}$, the total moisture content max. 10 % by weight and the ash content max 1.5 %. Moreover the briquettes must guarantee 9 months of the minimum storability. During this time the changes of briquettes size, density and moisture content must not exceed the limit of 10 %. The tested briquettes were made from spruce sawdust. For the briquettes production the briquetting press of the firm Brikliis (Malšice, Czech Republic),

type BrikStar 30-12, pressure chamber diameter of 50 mm, was used. All briquettes were made at the briquetting parameters constant adjustment.

Briquettes were divided into four groups and deposited in following storage spaces:

- Storage space I – in closed heated room, in plastic net bag and in plastic bag,
- Storage space II – in closed unheated room, in plastic net bag and in plastic bag.

Plastic net bags (so called raschel bags) are universal packaging material. They are lightweight, strong and breathable. They are used e.g. for storage of vegetables (potatoes, onions, carrots), fruit (apples, oranges), lump wood, wood chips etc.

Plastic bags have universal use. Bags were made from LDPE (low density polyethylene) with a thickness of 150 microns. They have high strength, stored material protects from moisture and dust.

The properties changes of briquettes for energy purpose have been studied by BROŽEK (2013A, 2014) and NOVÁKOVÁ AND BROŽEK (2016). They proved that during the briquettes storage their properties changed already after several months. At the briquettes storage in the closed heated room the changes are smaller than at their storage in the closed, but unheated room. But the radical influence occurs at storage in the closed plastic bag and in the plastic net bag.

After sampling the briquettes were numbered, weighted and their length and diameter measured. Then single briquettes were loaded by pressure using the universal tensile strength testing machine (Fig. 1). The test is finished at the briquette rupture, which is accompanied with the rapid load decrease. From the

load indicator the maximum load is taken down (BROŽEK, 2013B).

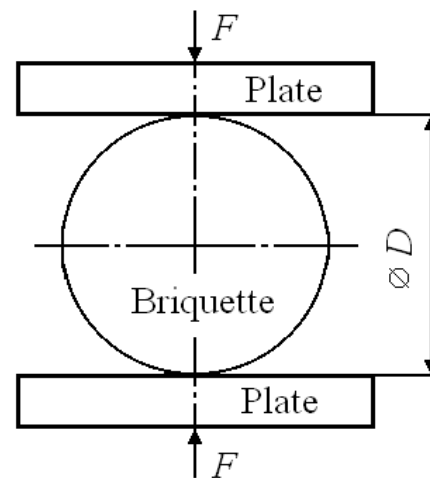


Fig. 1. – Principle of the plate-loading test

From the measured values the briquettes density was calculated. With regard to the production technology the briquettes are of different length. Therefore their rupture force was recalculated and it is presented as the force per unit.

The determination of the mechanical durability according to ČSN EN 14961-1 (2010) and ČSN EN 15210-2 (2011) was the part of carried out test. This test simulates the effect of transportation to change the properties of briquettes. Moreover the gross calorific value according to ČSN EN 14918 (2010), the ash content according to ČSN EN 14775 (2010) and the total moisture content according to ČSN EN 14774-2 (2010) were determined.

RESULTS AND DISCUSSION

The gross calorific value ($19.3 \text{ MJ}\cdot\text{kg}^{-1}$) of spruce sawdust, used for briquettes production, was determined according to ČSN EN 14918 (2010). The ash content (0.40 %) was determined according to ČSN EN 14775 (2010).

The test results are presented in Fig. 2, Fig. 3 and Tab. 1. Fig. 2 presents the relationship between rupture force and density (for new briquettes). Fig. 3 presents the relationship between rupture force and density (for all tested briquettes; the average values from all measurements are plotted). In Fig. 2 and Fig. 3 the standard deviation is demonstrated by the line segments. All measured values were evaluated statistically (see Tab. 1).

From Fig. 3 and Tab. 1 it is evident that the briquettes density decreased after three years storage that is regardless of the storage space and manner. The insignificant density decrease (of 0.6 %) was determined at briquettes (sample B) stored in the plastic bag in the closed heated room (space I). Higher density decrease (of 8.1 %) was determined at briquettes (sample C) stored in the net plastic bag in the closed heated room (space I) and at briquettes (sample D) (of 8.6 %) stored in the plastic net bag in the unheated room (space II). On the contrary at briquettes (sample E) storage in the plastic net bag in the closed unheated room (space II) the significant density decrease occurred (of 22.7 %).

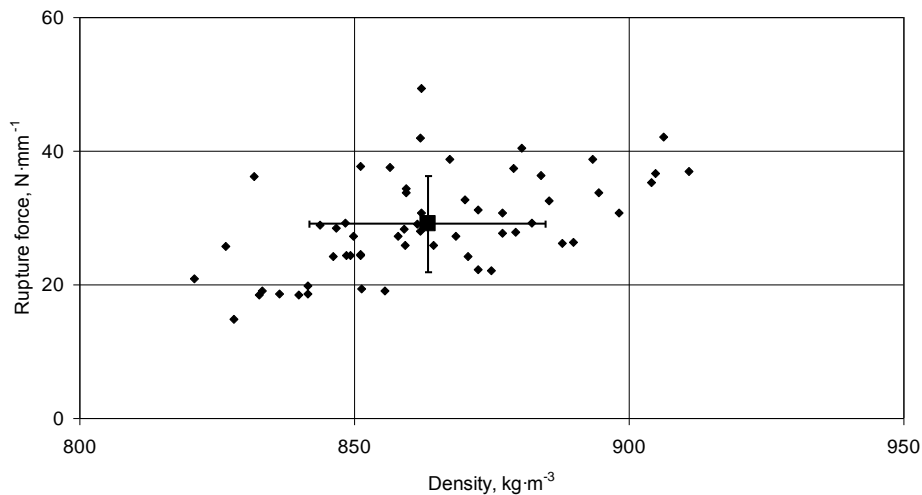


Fig. 2. – Relation between rupture force and density for briquettes stored in closed heated room in plastic net bag (sample C in Fig. 3; standard deviation is demonstrated by the line segments)

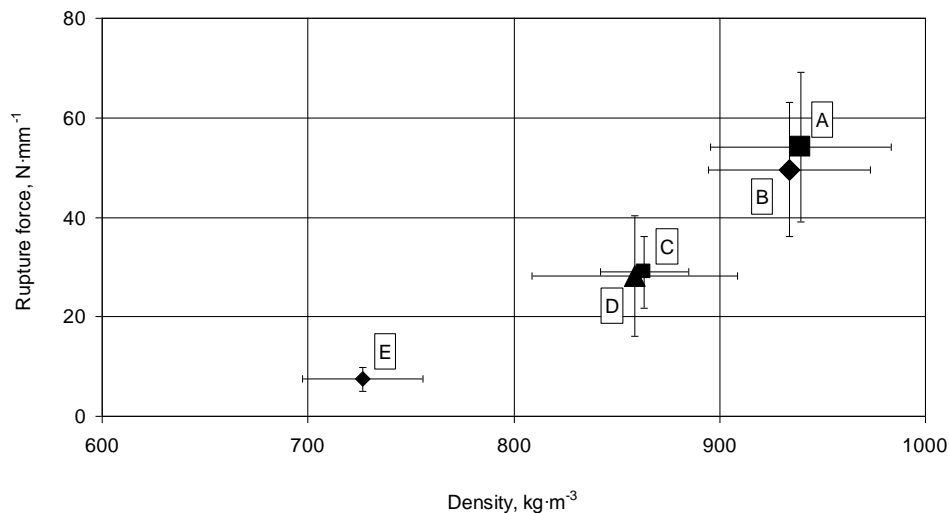


Fig. 3. – Relation between rupture force and density for all tested briquettes (standard deviation is demonstrated by the line segments): sample A – without exposure; sample B – storage space I, plastic bag; sample C – storage space I, plastic net bag; sample D – storage space II, plastic bag; sample E – storage space II, plastic net bag

Tab. 1. – Test results

Sample	Density (kg·m ⁻³)	Rupture force per unit (N·mm ⁻¹)	Mechanical durability (%)	Moisture content (%)
A: Without exposure	939.5 ± 43.7	54.1 ± 15.1	84.0 ± 3.1	7.3
B: Storage space I, plastic bag	934.0 ± 39.3	49.6 ± 13.5	83.8 ± 1.4	7.4
C: Storage space I, plastic net bag	863.5 ± 21.5	29.0 ± 7.2	75.5 ± 1.9	7.4
D: Storage space II, plastic bag	858.7 ± 49.8	28.2 ± 12.1	77.0 ± 6.3	8.0
E: Storage space II, plastic net bag	726.5 ± 29.2	7.5 ± 2.4	43.9 ± 4.2	11.4



Tab. 1. – Test results (continued)

Sample	Diameter (mm)	Length (mm)	Weight (g)
A: Without exposure	51.21 ± 0.21	57.01 ± 8.09	109.9 ± 13.0
B: Storage space I, plastic bag	51.72 ± 0.26	61.46 ± 7.05	120.3 ± 12.5
C: Storage space I, plastic net bag	52.27 ± 0.30	58.28 ± 5.61	107.9 ± 10.0
D: Storage space II, plastic bag	52.29 ± 0.44	60.39 ± 8.86	110.8 ± 14.3
E: Storage space II, plastic net bag	53.98 ± 0.68	69.86 ± 5.79	116.1 ± 9.9

Such results were determined at the rupture force. Although the Directive of the Ministry of the Environment of the Czech Republic No 14-2009 does not prescribe the watching of this parameter, the results are interesting.

After the briquettes storage in the plastic bag in the closed heated room (sample B) and at the plate-loading testing (Fig. 1) only the rupture force mild decrease (of 8.3 %) occurred, so that in this way stored briquettes meet the requirements also after three years storage. After storage in the plastic bag in the closed unheated room (sample D) the rupture force decrease (of 47.9 %) occurred. After storage in the net bag the rupture force decrease occurred, namely at their storage in the closed heated room (sample C, of 46.4 %) as well in the closed unheated room (sample E, of 86.1 %).

At the briquettes is different decrease in mechanical durability occur (Tab. 1). At the briquettes stored in space I in the plastic bag (sample B) of 0.2 %, in the plastic net bag (sample C) of 10.1 %. At the briquettes stored in space II in the plastic bag (sample D) of 8.3 %, in the plastic net bag (sample E) even of 47.7 %.

After the long-term storage the briquettes moisture changed, but relatively little. At three from four sam-

ples it was after three years lower than 8 %. Only at storage in the plastic net bag in the closed unheated room (sample E) it increased considerably, namely up to 11.4 %.

From the mentioned tests evaluation it follows that in the course of the long-term storage the briquettes loosening occurs. Their size (diameter, length) become larger, their density as well as the rupture force decrease (Tab. 1). Contemporarily their mechanical durability decreases. The change of the moisture content depends first of all on the storage location and conditions. In conclusion it is possible to state that briquettes degrade, at that practically all watched parameters get worse.

From the test results it follows that on the briquettes durability the storage time is of no substantial influence, but primarily they are their storage space and manner. According to the producer recommendation the dry and heated rooms can be considered as the suitable spaces. On the contrary unheated spaces are less suitable. Briquettes should be always stored in leak proof closed plastic containers.

The results published in this paper confirm the results published by BROŽEK (2013A; 2014) and by NOVÁKOVÁ AND BROŽEK (2016) for briquettes made from spruce shavings or birch chips.

CONCLUSIONS

In the paper the study results of three factors influencing the briquettes mechanical properties at the long-time storage are presented. The influence of the briquettes storage space (closed heated room, closed unheated room) was the first studied factor, the second the storage manner (plastic bag, plastic net bag) and the third the storage time (new briquettes, briquettes after three years storage). Density and rupture force were criterions for the briquettes evaluation. Contemporarily next parameters were also watched, namely

mechanical durability, moisture content, diameter, length and weight of briquettes.

By the carried out tests it was unambiguously proved that the manner of briquettes long-term storage is of the highest influence on their durability.

Briquettes, stored in the well closed plastic bag in the closed heated room (space I, sample B), changed their properties after three years only little. The density decreases of 0.6 %, the mechanical durability of 0.2 % and the rupture force of 8.3 %. Briquettes, stored in



the same place, but in the plastic net bag (sample C), changed their properties substantially more. Clearly it was evident from the value of rupture force which decreased of 46.4 %. The density decreased of 8.1 %, the mechanical durability of 10.1 %.

Briquettes, stored in the closed, but unheated room (space II), changed their properties after three years very considerably. At their storage in the plastic bag (sample D) the decrease in density of 8.6 %, mechanical durability of 8.3 % and rupture force of 47.9 % occurred. At their storage in the plastic net bag (sample E) the decrease in density of 22.7 %, mechanical

durability of 47.7 % and rupture force of 86.1 % occurred. These briquettes were practically unusable.

On the basis of the carried out tests it follows that for the briquettes quality evaluation it is possible to recommend the parameter rupture force.

From the above mentioned conclusions it follows that briquettes should be always stored in leak proof well closed plastic containers. If briquettes are by their producers supplied in different containers or even in bulk it is without delay necessary to transfer them into suitable containers. Only in this way it is possible to guarantee their demanded properties also after three years storage, too.

ACKNOWLEDGEMENTS

Supported by the Internal Grant Agency of the Faculty of Engineering, CULS Prague, Prague, Czech Republic IGA 2016: 31140/1312/3107 "Influence of feedstock specific mechanical parameters and type of storage conditions on final quality of briquettes from waste biomass".

REFERENCES

1. BASORE, C. A.: Fuel Briquettes from Southern Pine Sawdust. Auburn, Alabama Polytechnic Institute 1929.
2. BROŽEK, M.: Quality evaluation of briquettes made from biomass. The Fifth International Scientific Conference Rural Development 2011. 24-25 November 2011. Akademija, Aleksandras Stulginskis University, pp. 308-313.
3. BROŽEK, M., NOVÁKOVÁ, A., KOLÁŘOVÁ, M.: Quality evaluation of briquettes made from wood waste. Res. Agr. Eng., 58, 2012: 30-35.
4. BROŽEK, M.: Study of briquettes properties at their long-time storage. Journal of Forest Science, 59, 2013a: 101-106.
5. BROŽEK, M.: Properties of briquettes from paper waste. Manufacturing Technology, 13, 2013b: 138-142.
6. BROŽEK, M., NOVÁKOVÁ, A.: Briquettes from recovered paper and board. 12th International Scientific Conference Engineering for Rural Development. 24-25 May 2013. Jelgava, Latvia University of Agriculture, pp. 488-493.
7. BROŽEK, M.: Influence of storage on briquettes mechanical properties. Scientia Agriculturae Bohemica, 45, 2014: 175-179.
8. NOVÁKOVÁ, A., BROŽEK, M.: Briquettes properties after three years storage. 15th International Scientific Conference Engineering for Rural Development. 25-27 May 2016. Jelgava, Latvia University of Agriculture, pp. 80-85.
9. OTTO, J.: Ottův slovník naučný (Otto's encyclopaedia). Vol IV. Prague, J. Otto, 1891.
10. PLÍŠTIL, D., BROŽEK, M., MALÁŤÁK, J., HENEMAN, P.: Heating briquettes from energy crops. Res. Agr. Eng., 50, 2004: 136-139.
11. STEHLÍK, V. ET AL.: Naučný slovník zemědělský (Encyclopaedia agricultural). Vol I. Prague, ÚVTI 1966.
12. TEAM OF AUTHORS: Všeobecná encyklopedie (General encyclopaedia). Vol I. Prague, Diderot 1999.
13. TEAM OF AUTHORS: The New Encyclopaedia Britannica. Index A-K. 15th Ed. Chicago, Encyclopaedia Britannica 1991.
14. DIRECTIVE OF MINISTRY OF ENVIRONMENT: No. 14-2009. Brikety z dřevního odpadu (Briquettes from Wood Waste). Prague, Ministry of Environment of the Czech Republic. 2009.
15. ČSN 42 0030: Ocelový a litinový odpad (Steel and cast iron scrap). 1994.
16. ČSN 42 1331: Odpady neželezných kovů a jejich slitin (Scraps from nonferrous metals and their alloys). 1991.
17. ČSN EN 14774-2: Tuhá biopaliva – Stanovení obsahu vody – Metoda sušení v sušárně – Část 2: Celková voda – Zjednodušená metoda (Solid biofuels – Determination of moisture content – Oven dry method – Part 2: Total moisture – Simplified method). 2010.
18. ČSN EN 14775: Tuhá biopaliva – Stanovení obsahu popela (Solid biofuels – Determination of ash content). 2010.
19. ČSN EN 14918: Tuhá biopaliva – Stanovení spalného tepla a výhřevnosti (Solid biofuels – Determination of calorific value). 2010.
20. ČSN EN 14961-1: Tuhá biopaliva – Specifikace a třídy paliv – Část 1: Obecné požadavky (Solid biofuels – Fuel specifications and classes – Part 1: General requirements). 2010.
21. ČSN EN 15210-2: Tuhá biopaliva – Stanovení mechanické odolnosti pelet a briket – Část 2: Brikety (Solid biofuels – Determination of mechanical durability of pellets and briquettes – Part 2: Briquettes). 2011.

Corresponding author:

Alexandra Nováková, Department of Material Science and Manufacturing Technology, Faculty of Engineering, Czech University of Life Sciences Prague, Kamýcká 129, Praha 6, Prague, 16521, Czech Republic, phone: +420 22438 3308, e-mail: novakovaa@tf.czu.cz